

Preparation and characterization of bioactive silica derived from Rice husk supported TiO₂ and cobalt nanocomposite via sol – gel route

A.Ananthi^a, K.Kapildev^b

^{a,b}Department of physics, Annamalai University, M.R.K. Arts and Science college, Kattumannar kovil (TK) ,
608301

Email: ananthi5arumugam@gmail.com

Abstract:

In the present study, amorphous silica nano particles were taken from low cost rice husk by carrying out an acid treatment by the process of heat treatment. Silicon precursor was obtained in the form of sodium silicate rice husk ash. Sodium silicate solution was obtained by direct silica extraction from rice husk via solvent extraction method without adding any template. The target nano composite (RHS/TiO₂/Co) was formed by embedding the cobalt nanoparticles into SiO₂/TiO₂. The prepared samples were characterized by XRD, FTIR, SEM/EDS, TG-DTA, UV and TEM. The cobalt was found to isomorphously substitute in the silica matrix. A good dispersion of cobalt nanoparticles was evidenced by X-ray diffraction. Scanning electron microscopy confirmed the formation of well dispersed and spherical cobalt nanoparticles. During TGA analysis, it was observed that, mass trace suddenly goes backwards along the abscissa and then continues forward normally. This technique provided an environmentally friendly production process for conversion of waste rice husk to high performance materials.

DOI: 10.7176/CMR/18-1-02

Publication date: February 28th 2026

Introduction:

Increased environmental consciousness has motivated research into the effective utilization of agricultural byproducts. Rice husk is an important agricultural waste that abundantly produced globally every year. Due to its high silicon content, rice husk has become a Source for preparation of elementary silicon and a number of silicon compounds, especially silica (sodium silicate) [1], silicon carbide [2] and silicon nitride [3]. Silica is the major inorganic constituent of the rice husk, which by carrying out an acid chemical treatment followed by the process of burning; it is possible to extract high-surface area amorphous silica. Recently, Adam et al. managed to incorporate various types of transition metals into rice husk silica and reported their catalytic potentials in the oxidation, acylation and benzoylation reactions [4–6]. Among known transition metals, cobalt undoubtedly has gained wide interest in numerous catalytic studies. For example, cobalt nanoparticles supported on silica in steam reforming ethanol, CoFe₂O₄ and Co₃O₄ nanocrystals as heterogeneous catalyst for cyclohexane oxidation and also methane combustion. Owing to its broad applications, various methods have been employed by researchers to produce unique Co or Co bimetallic nanoparticles which includes thermal decomposition, pulsed laser irradiation chemical vapor condensation (CVD) [7], co-precipitation, reversed micelle technique reduction of cobalt chloride and thermolysis [8]. Most recently, a ferromagnetic cobalt nanoparticle between 35-200 nm size range was successfully synthesized by a modified polyol technique [9]. Additionally, cobalt nanoparticles were synthesized by reverse microemulsion consisting of either neutral or ionic surfactants [10]. Furthermore, Fu and co-workers [11] have developed spherical core cobalt/silica nanoparticles by activated plasma evaporation of the metal.

However, most of these existing procedures are expensive, complicated, time consuming and involves organic solvents. For instance, thermal decomposition methodology requires long period of calcination and high temperature as reported by Yang *et al.*, [12]. Silica is an inert support material with a high surface area. It has been widely used in ceramics and electronics. Rice husk, an abundantly available agricultural waste has emerged as an ideal source of high grade amorphous silica. Many studies have been reported on the use of silica from rice husk as a catalyst support. Sol-gel process is claimed to be a simple and effective synthesis pathway for the production of nanomagnetite, silica nanotubes and nanocomposites [13]. Thus, this study a simple and sol – gel route to synthesize cobalt nano particles supported on rice husk silica/TiO₂ with unique morphology and structural properties.

Materials

All the chemicals used were analytical grade. Titanium isopropoxide (Ti(OC₃H₇)₄ 97%) was used as a precursor of titania and Cobalt nitride (Co(NO₃)₂.6H₂O) as dopant sources. Other materials used were nitric acid and sodium hydroxide pellets. Rice husk gathered from agriculture department, Annamalai University. All the chemicals used directly without further purification. Methanol and distilled water were used as a solvent in sol – gel process.

Characterization

Powder X-ray diffraction pattern was obtained from a Rigaku miniflex diffract meter for 2 θ values from 10⁰ to 90⁰ using CuK α target at wavelength of $\lambda = 1.5406 \text{ \AA}$. The FTIR analysis was carried out in a Perkin Elmer Spectrum 1000 using the KBr pellet method. The UV-Vis spectra were recorded with a Hitachi, UV3501 spectrometer. Scanning electron microscopy (SEM), (JEOL – JSM – 6360LV) was used to record the morphology of the prepared materials and the elemental analysis was carried out by energy dispersive analysis (EDX) and Treated rice husk ash TGA and DTA analysis were performed in thermo gravimetric equipment (Pyris7, Perkin – Elmer).

Experimental Procedures


Preparation of Rice Husk Ash

Preparation of rice husk ash is done by cleaned and washed with distilled water. The cleaned 100 gm rice husk was shocked in 500 ml of 3M HNO₃ and the mixture was stirred for 3 hours at 80⁰C temperature. After the reflux, the solids are washed with de ionized water until neutral (acid free) and dried at a temperature of 120⁰C overnight. Rice husk that have been dried and then calcined at temperature of 700⁰C for 5 hours.


Preparation of silica gel nano particles

5g rice husk ash was mixed with 250mL of 1N sodium hydroxide aqueous solution. The mixture was refluxed for 3h at 110⁰C. The solution was filtered and stored in a refrigerator for further usage [14]. A 5ml sample of sodium silicate solution was taken from the stock solution and poured into 15ml distilled water at a time and stirred for a specific time. The pH of the solution was adjusted to 10-12 by drop wise addition of hydrochloric acid under stirring speed to form silica gel. The time want for gelation is approximately within five minutes after

sol solution was neutralized. Agitation was continued for another one hour to obtain wet gel nano particles. The prepared gel was aged at 700°C for 3h under finalized condition. Distilled water, NaCl and other impurities were separated from the gel by solvent exchange with dilute and pure methanol in 4-5 times. The dilute methanol (75%) was used to avoid any structural shrinkage during the solvent exchange. Completely, methanol exchange was done six times and aged at 700°C. The total time of aging was 52 h. The wet gels were then dried [15]. The final product labeled at RH-Silca.



During the addition of sulphuric acid, Si-OH formed and condensed to form siloxane bond as shown below



Synthesis of RHS doped Titania:

The synthesis of titania – silica nano composites was prepared by sol – gel method. The molar ratio of silica to titania sols was 0.5:0.02. The Stock solution was added to titania solution while stirring for 5 hr until a gel was formed. The gel was aged for 24 hrs and then rinsed with water followed by heating at 150°C for 5 hrs. Finally the solution was filtered at whatmann filter paper and dried was kept at oven. The final product was labeled at RHS-TiO₂.

Synthesis of RHS/TiO₂/Co nano composites:

The preparation of RHS/TiO₂ nano composites doped nickel by using sol – gel technique. The Stock solution was added to titania (0.5:0.02) solution while stirring for 30 minutes and immediately added to cobalt solution (varying concentrations are 0.5,1.0,1.5%) within a fraction of time the gel was formed. The wet gel was dried kept at hot air oven. The finally product labelled RHS/TiO₂/Co

Phase Investigation and structural analysis:

The X-ray spectra and characteristic absorption peak of RHS have been acquired and displayed in Fig 1 (a), the sample is entirely amorphous as pointed out by the featureless diffractograms and the appearance of a scatter maximum at $2\theta = 23^\circ$ characteristic for amorphous silica [16]. This pattern exhibits a very broad line and no defined peaks due to crystallinity were encountered. On the figure 1(a) are also described the theoretical postures of the main reflexion of the phase cristobalite (SiO₂) and graphite (C) and no peaks were discovered in these postures. The results obtained conceded to conclude that the ash produced has an amorphous structure.

RHS doped TiO₂

In Fig 1 (b) RHS doped with TiO₂ (1:1) agrees the presence of peak $2\theta = 25.28^\circ$ corresponding to (101) plane and it is the characteristic peak of anatase (JCPDS 21-1272). Strong diffraction peaks at 25° and 48° indicating TiO₂ in the anatase structure. There is no any spurious diffraction peak found in the sample. The peak intensity of the sample reflects that the formations of nanoparticles are crystalline. Amorphous disclosed a broad pattern with low intensity. Silica can exhibit the formation anatase by impeding direct contact between TiO₂ particles forming the Ti – O – Si binding [16]. The diffractogram clearly suggesting that only anatase phase has been

formed. The use of TiO₂ in the silica matrix of 50% will reduce the anatase phase and forming amorphous TiO₂ – SiO₂ [17].

Cobalt doped RHS/TiO₂

In Fig 1 (c-e) RHS- TiO₂ doped cobalt (0.5, 1.0 and 1.5 % wt) respectively. The peak relatively (311) plane and the corresponding angle $2\theta = 35.41^\circ$ (JCPDS 43 – 1003) was used for finding the particle size of the formed oxide; an average dimension 38nm was calculated. The presence of Co₃ O₄ and CoO can be further analysed from XRD spectra.

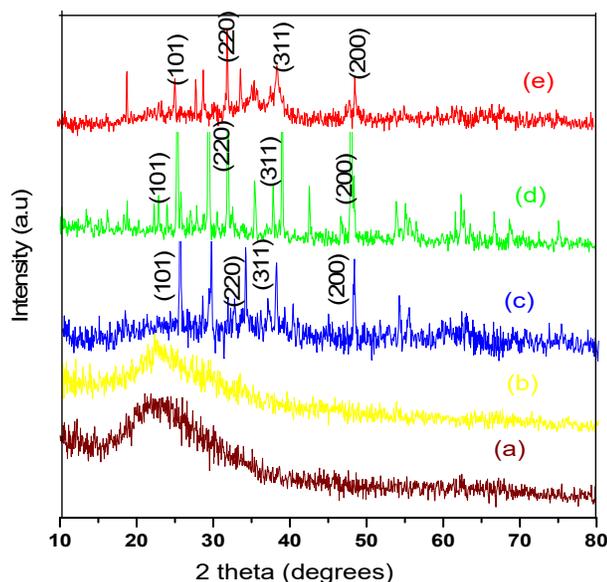


Fig1 XRD pattern of a) RHS b) RHS/TiO₂ c) RHS/TiO₂/0.5 Co d) RHS/TiO₂/1.0 Co
 e) RHS/TiO₂/1.5 Co

Moreover, it is worth nothing that the amorphous structure of silica present in our sample remained and no peaks corresponding to the transition metal oxides are also observed. This implies that cobalt is still well dispersed in the titania – silica framework [18]. Smaller co particles undetected in the XRD may also lead to untraceable crystalline peaks. Reflections corresponding to Co could not be observed which could be due to the overlap with other signals or broadening of the XRD peak.

Table 1. Particle size and Dislocation density of the Nano Composites

Sample Name	Particle size (Debye) nm	Particle size (W-H plot) nm	Strain Unit less	Dislocation Density (m ²)
RHS	50.42	69.32	0.002	0.638 X 10 ⁻¹⁵
RHS/TiO ₂	22.04	54.32	0.002	0.541 X 10 ⁻¹⁵
RHS/TiO ₂ /0.5% Co	43.84	78.78	0.001	0.176 X 10 ⁻¹⁵
RHS/TiO ₂ /1.0% Co	39.02	54.34	0.002	0.471 X 10 ⁻¹⁵
RHS/TiO ₂ /1.5% Co	38.03	27.73	0.005	0.919 X 10 ⁻¹⁵

This is in agreement with titania promoted silica assisted cobalt catalyst subjected to air drying out 150°C which showed decomposition of cobalt nitrate into intermediate cobalt silicate phase and finally the product was labelled at RHS-TiO₂-Co.

Spectral studies:

Fig 2 (a) shows an FTIR spectrum at RHS. A broad band in the range of 3362 cm⁻¹ is due to the stretching vibration of the O – H band. This band is due to silanol groups (Si – OH) and the adsorbed water bound to the surface. The weak band 1642 cm⁻¹ is assigned to H – O – H bending vibrations mode where also represented due to the adsorption of water in air when FTIR samples disk were prepared in an atmospheric pressure. Also, there is a tiny dip in the spectra at 2354 cm⁻¹ due to the presence of atmospheric CO₂. These peaks are trapped in the matrix of silica surface. The predominant peak at 1383 cm⁻¹ is due to siloxane bonds (Si – O – Si). The adsorption bands between 474 and 993 cm⁻¹ are because of silica structures and other peaks observed in the range of 1247 and 2764 cm⁻¹ are because of impurities such as carbonate and sodium groups. The peaks between 1055 and 711 cm⁻¹ indicates the vibration modes of Si – O – Si network. A most intense band at 1110 cm⁻¹ and a peak 765 cm⁻¹ are due to asymmetric and symmetric stretching mode at Si – O – Si. The bending vibration of Si – O is shown by strong band at 475 cm⁻¹. The vibration of oxygen atoms joined with the adjacent atoms in the asymmetric stretching vibrations of Si – OH bond appeared at 1150 cm⁻¹ [19].

RHS doped TiO₂

In Fig 2 (b) the presence of some weak transmittance bands between 3362 & 3467 and at a 1634 are seen, which are gradually decreased with TiO₂ doping concentrations. An intense band at 606 and 852 cm⁻¹ is seen which is attributed to different vibrational modes of TiO₂. The intense band below 1343 cm⁻¹ is due to Ti – O – Ti vibrations. The shift in lower wave numbers and sharpening of the Ti – O – Ti band width increase of TiO₂ concentration could be attributed to the decrease of particle size. The band 835 cm⁻¹ are mainly ascribed to Ti-O and Ti – O – O bonds. According to the FTIR spectrum, the sample containing SiO₂:TiO₂ equal to 50:50 obviously shows the presence of Ti – O – Si bonding.

Cobalt doped RHS/TiO₂

In fig 2(c-e) Cobalt doped with RHS/TiO₂ (0.5, 1.0 & 1.5%wt) respectively. The band at 990 cm⁻¹ RHS disappeared after introducing cobalt into silica framework. The change in intensity with increasing Co concentration indirectly substitution of cobalt ions in the silica framework. Replacement of Si with Co results in a decrease in the intensity of the 990 cm⁻¹ band showing the replacement of the Si – O – H groups with Si – O – Co groups. inset spectrum fig 6(a) clearly demonstrates band at 646 cm⁻¹ for RHS – Co which is absent in RHS. The 646 cm⁻¹ is described to spinel type Co – O bond corresponding to Co₃O₄. It confirms the M- O stretching vibration in which Co²⁺ is tetra hedrally coordinated. The nitrate group has six normal vibrations that are IR active.

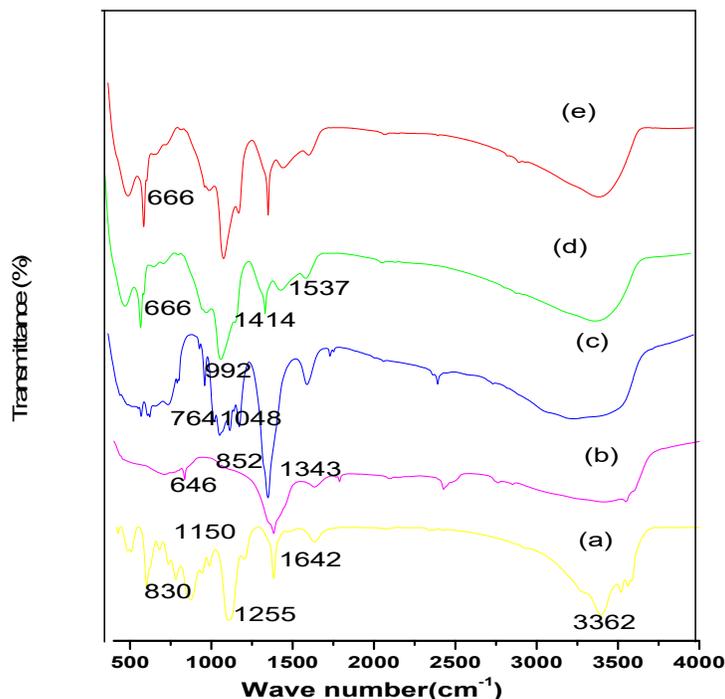


Fig2. FTIR spectra of a) RHS b) RHS/TiO₂ c) RHS/TiO₂/0.5 Co d) RHS/TiO₂/1.0 Co e) RHS/TiO₂/1.5 Co

These are the anti symmetric stretching, out of plane bending, anti symmetric in plane bending and the symmetric in plane bending observed at 1519, 1362, 1045, 825, 780 and 646 cm⁻¹ respectively [20]. Meanwhile, unobvious peaks in the range 400 – 1500 cm⁻¹ attributed to the anatase phase are found in this sample. No significant differences were observed at the spectra which repeatedly confirm the formation of cobalt nano particles

Thermal Studies:

In this experiment with linear heating at 10°C/min, the TG curve are analysed the gas of sample with decomposition from atmosphere as shown in fig (3). The TG spectra observed that in the 200°C to 280°C. The initial weight loss should be decomposition of CoO(OH) according to the equation



Above 600°C, the weight remained constant confirming the complete decomposition of the RHS/TiO₂/Co nano composites [21].

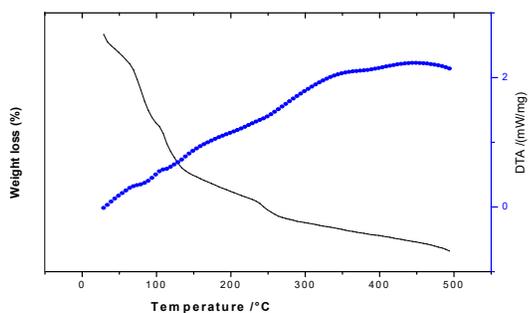


Fig 3. TG/DTA curve RHS/TiO₂/Co

Morphology Studies:

Fig 4 (A) & (B) exhibits the SEM and EDX analysis Rice husk silica. In SEM image, RHA particles are polygonal shape with different sizes. A strong intensity of Si in the EDS spectrum is confirmed the silica at higher weight percentage Fig 4 (C) & (D) show SEM characterization of titania – rice husk silica. The images had small grains without clear boundaries. The forming competition between silica and titaniaanatase phase, can cause the agglomeration [22]. Silica in amorphous phase prevents the formation of grain boundaries of titania and silica. It reveals that the presence of Ti, O and Si are the only elementary species in the sample [23]. The surface morphological features of synthesized Nickel doped RHS/TiO₂ nano composites were studied by SEM in Fig 4 (E) & (F). The instrumental parameters, accelerating voltage, spot size magnification and working distances are indicated on SEM images. The observed SEM images exhibits that the particles are spherical and are polycrystalline. This infers that the addition of cobalt does not affect the crystal structure which confirms the incorporation of cobalt in to Ti lattice site. While increasing the doping concentration the particle size was

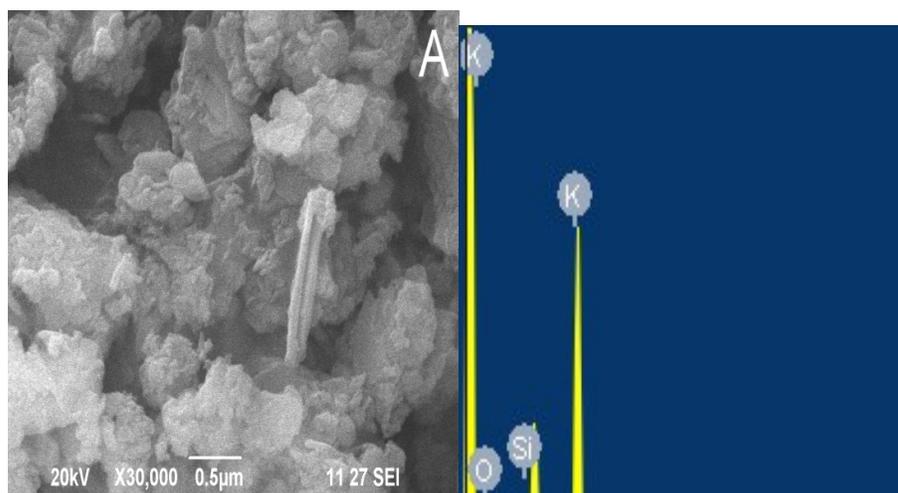


Fig 4 (A) SEM image of RHS

(B) EDS spectrum of RHS

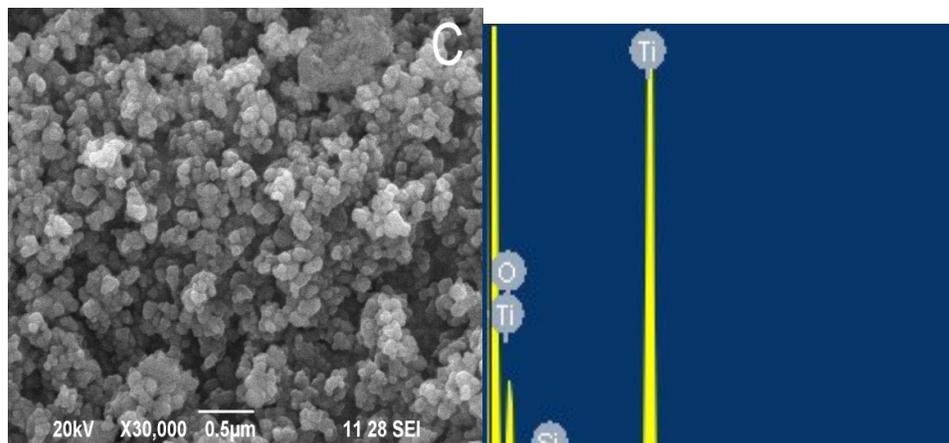


Fig 4(C) SEM image of RHS/TiO₂ (D) EDS spectrum RHS/TiO₂

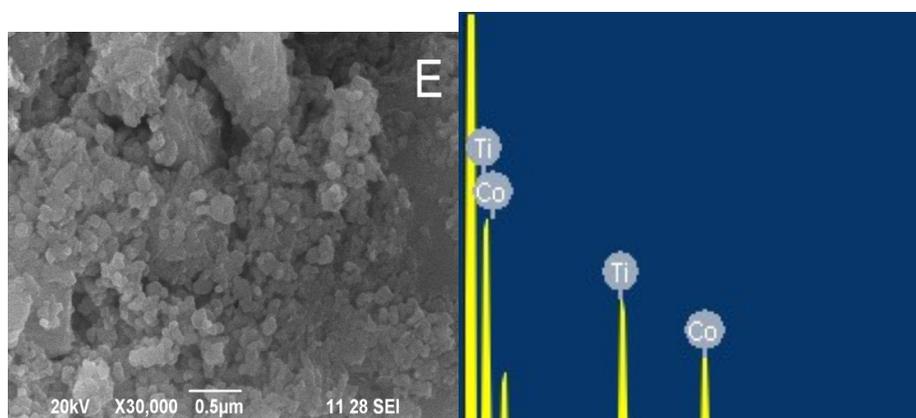


Fig 4(E) SEM image of RHS/TiO₂/Co (F) EDS spectrum RHS/TiO₂/Co

Considerably reduced and aggregated. The EDX spectrum for RHS/TiO₂ and 1.5%Co nano composites are shown in Fig 16 (b). The figure reveals that the presences of Ti, O, Si and Co are the only elementary species in the sample. Moreover, no additional peaks were observed (30).

Optical Studies:

Fig (5) exhibits the relation between absorbance and wavelength for cobalt doped RHS/TiO₂. It can be obtained that the absorbance increases with wavelength in the range of 550 nm and then followed suddenly slow at higher wavelengths. The spectrum exhibits high transmittance in the visible and infrared regions and absorption edge is sharp in the visible region [24]. The DR UV – Vis spectroscopy was known to be a sensitive probe for the identification and characterization of metal ion concentration and its existence in the framework and/or in the extra framework position of metal containing nano composites. Fig shows two bands with the maxima near and nm attributed to the O²⁻ Ti⁴⁺.

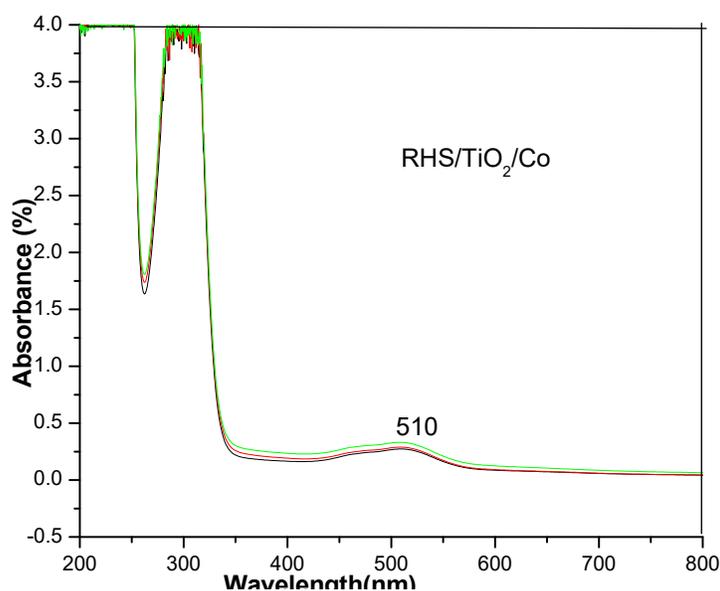


Fig 5 UV – Vis spectrum RHS/TiO₂/Co

Conclusion:

Cobalt nano particles were synthesized via simple sol – gel route under mild conditions. This simple approach resulted in the successful generation of spherical and polycrystalline cobalt nano particles. The characterization of FTIR and XRD reveals the presence of CoO, Co₃O₄ and Co – silicate hydroxide in the material. Characteristic peaks for cobalt and cobalt oxide were not present in the XRD patterns for Co – doped Rice husk silica /TiO₂ nano composites, indicating that the doped copper was well distributed and amorphous. UV absorption for the 0.5, 1.0 and 1.5 wt% Co - doped Rice husk silica /TiO₂ was observed at 485,490 and 510nm.

References:

1. Fleaca, C.T.; Morjan, I.; Alexandrescu, R.; Dumitrache, F.; Soare, I.; Gavrila-Florescu F. Le Normand, L.; Derory, A. Magnetic properties of core-shell catalyst nanoparticles for carbon nanotube growth. *Appl. Surf. Sci.*, **2009**, *255*, 5386-5390.
2. Cheng, G.; Walker, A.R.H. Synthesis and characterization of cobalt/ gold bimetallic nanoparticles. *J. Magn. Mater.*, **2007**, *311*, 31-35.
3. Tong, J.; Bo, L.; Li, Z.; Lei, Z.; Xia, C. Magnetic CoFe₂O₄ nanocrystal: A novel and efficient heterogeneous catalyst for aerobic oxidation of cyclohexane. *J. Mol. Catal. A: Chem.*, **2009**, *307*, 58- 63.
4. Kalyan Kamal, S.S.; Sahoo, P.K.; Premkumar, M.; Rama Rao, N.V.; Jagadeesh Kumar, T.; Sreedhar, B.; Singh, A.K.; Ram, S.; Chandra Sekhar, K. Synthesis of cobalt nanoparticles by a modified polyol process using cobalt hydrazine complex. *J. Alloys Compd.*, **2009**, *474*, 214-218.

5. Deng, Y.-H.; Wang, C.-C.; Hua, J.-H.; Yang, W.-L.; Fu, S.-K Investigation of formation of silica-coated magnetite nanoparticles *via* sol-gel approach. *Colloid Surf. A.*, **2005**, *262*, 87-93.
6. Ribeiro, R.U.; Liberatori, J.W.C.; Winnishofer, H.; Bueno, J.M.C.; Zanchet, D. Colloidal Co nanoparticles supported on SiO₂: Synthesis, characterization and catalytic properties for steam reforming of ethanol. *Appl. Catal. B.*, **2009**, *91*, 670-678.
7. Zhou, L.; Xu, J.; Miao, H.; Wang, F.; Li, X. Catalytic oxidation of cyclohexane to cyclohexanol and cyclohexanone over Co₃O₄ nanocrystals with molecular oxygen. *Appl. Catal. A.*, **2005**, *292*, 223-228.
8. Ren, L.; Wang, P.; Han, Y.; Hu, C.; Wei, B. Synthesis of Co₂O₄.2H₂O nanorods and their thermal decomposition to Co₃O₄ nanoparticles. *Chem. Phys. Lett.*, **2009**, *476*, 78-83.
9. Salavati-Niasari, M.; Khansari, A.; Davar, F. Synthesis and characterization of cobalt oxide nanoparticles by thermal treatment process. *Inorg. Chim. Acta*, **2009**, *362*, 4937-4942.
10. Yang, H.T.; Shen, C.M.; Wang, Y.G.; Su, Y.K.; Yang, T.Z.; Gao, H.J. Stable cobalt nanoparticles passivated with oleic acid and triphenylphosphine. *Nanotechnology*, **2004**, *15*, 70-74.
11. Robinson, I.; Volk, M.; Tung, L.D.; Caruntu, G.; Kay, N.; Thanh, N.T.K. Synthesis of Co nanoparticles by pulsed laser irradiation of cobalt carbonyl in organic solution. *J. Phys. Chem. C.*, **2009**, *113*, 9497-9501.
12. Wang, Z.H.; Choi, C.J.; Kim, J.C.; Kim, B.K.; Zhang, Z.D. Characterization of Fe-Co alloyed nanoparticles synthesized by chemical vapour condensation. *Mater. Lett.*, **2003**, *57*, 3560-3564.
13. Adam F, Andas, J. Amino benzoic acid modified silica – An improved catalyst for the mono-substituted product of benzylation of toluene with benzyl chloride, *J. colloid interface*, (2007), 135-143.
14. Kalapathy U, A. Proctor, J. Shultz, A simple method for production of pure silica from rice hull ash, M. Chareonpanich, *Bioresour. Technol.* *73* (2000) 257–262.
15. Della V.P., I. Kühn, D. Hotza, Rice husk ash as an alternate source for active silica production, *Mater. Lett.* *57* (2002) 818–821.
16. Watari J, A. Nakata, T. Torikai, M. Yada, Fabrication of porous SiO₂/C composite from rice husks, *Journal of the European Ceramic Society* *26* (2006) 797–801.
17. Conradt R, P. Pimkhaokham, U. Leela-Adisom, Nano-structured silica from rice husk, *Journal of Non-Crystalline Solids* *145* (1992) 75–79.
18. Park B.D., S. Wi, K. Lee, A. Singh, T.-H. Yoon, Y. Kim, Characterization of anatomical features and silica distribution in rice husk using microscopic and micro-analytical techniques, *Biomass and Bioenergy* *25* (2003) 319–327.
19. Ayhan, Demirbas, A discussion of the paper “Study on the pozzolanic properties of rice husk ash by hydrochloric acid pre-treatment” by Q. Feng, H. Yamamichi, M. Shoya, S. Sugita, *Cement and Concrete Research* *35* (2005), 1017.
20. Yuvakkumar R, V. Elango, V. Rajendran & N. Kannan, High-purity nano silica powder from rice husk using a simple chemical method, *Journal of Experimental Nanoscience*, (2014).
21. Nabeel A. Bakr*, Sabah A. Salman, Ahmed M. Shano, Effect of Co Doping on Structural and Optical Properties of NiO Thin Films Prepared By Chemical Spray Pyrolysis Method, *International Letters of Chemistry, Physics and Astronomy*, *11*, 2014, 15-30.

22. .Rajinder Kumar, Ragini Raj Singhand P. B. Barman, COBALT DOPED NICKEL ZINC FERRITE NANOPARTICLES – XRD analyses an insight , International Journal of Scientific & Engineering Research, 5(5),(2014).
23. Theivasanthi T, and M. Alagar , X –ray diffraction studies of copernano powder,.
24. ThirugnanasambandanTheivasanthi* and MarimuthuAlagar, Titanium dioxide (TiO₂) Nano particles – XRD Analyses – An sight.
25. . SelvarajVentakeswaran, Ratinamyuvakumar and Venkatachalamrajendran, Nano silicon from nano silica using natural resource (Rha) for solar cell fabriciation, Phosphorus, sulphur and silicon and the related elements, (2013), 1178-1193.